ISSN: 2582-4686 SJIF 2021-3.261,SJIF 2022-2.889,
2024-6.875 ResearchBib IF: 9.948 / 2024

THE MULTIDISCIPLINARY JOURNAL OF SCIENCE AND TECHNOLOGY

VOLUME-5, ISSUE-3

STUDYING THE SYNTHESIS OF ANTIOXIDANTS BASED ON GOSSYPOL AND EPICHLOROHYDRIN

[1] Shamaev B.E., [2] Nomozov A.K., Eshkoraev S. S.

[2] Associate professor of Department of Chemical Engineering, Termez State University of Engineering and Agroechnologies. Termez, Uzbekistan,190111.

Abstract. In this paper, the study of a new antioxidant based on gossypol with epichlorohydrin (ECH) was carried out in two ways: in the presence of 1% phosphoric acid and 0.5% alkali solution in a molar ratio of gossypol: alkali=1:2. Obtained in the presence of phosphoric acid, has the following characteristics: it is a homogeneous brown powder, average molecular weight 2300-3500, non-volatile, main component content 99.6% and in an alkaline environment, has the following characteristics: uniform brown powder, average molecular weight 2500-3800, non-volatile, main component content 99.7%. The technological regime of the optimal conditions for the synthesis of gossypol with epichlorohydrin is carried out at a molar ratio of 1:1 in the temperature range of 313–353 K in an alcohol solution. The structure of this compound was confirmed by IR, ^{1}H NMR, spectral and elemental analysis. For comparison, IR spectra of gossypol and its oligomeric derivatives GECH were taken. This obtained oligomer was applied to polyethylene as an antioxidant and improved its mechanical and thermal properties.

Keywords: gossypol, epichlorohydrin, antioxidant, elemental analysis, IR- analysis, ^{1}H NMR-analysis.

Abbreviations and notation: epichlorohydrin (ECH), gossypol and epichlorohydrin (GECH), gossypol and allyl halides (GAG), gossypol with allylthiourea (GATM), polyethylene (PE), low density polyethylene (LDPE).

Introduction.

Currently, there is an intensive growth in the production and use of polymer materials based on polyolefins and elastomers. At the same time, although they have valuable physicochemical properties, they have a significant drawback: polymer materials based on polyolefins and elastomers are subject to various types of aging under the influence of heat, light, oxygen, etc., and their properties are not always sufficiently stable. Therefore, one of the ways to increase the resistance of polymer materials to heat and oxygen is to introduce antioxidant stabilizers into them.

[1,2]. In recent years, foreign studies have also observed trends in replacing synthetic products with products of natural origin, the raw materials for the production of which are renewable resources [3,4], biological and chemical processes [5], the source of raw materials for the synthesis of which is waste from the wood processing industry (wood and bark of coniferous and deciduous trees) [6,7]. The introduction of a terpene substituent into the aromatic ring of phenols is possible through the interaction of phenols with terpene hydrocarbons, alcohols or halogen derivatives in the presence of acidic catalysts. In the presented work studied the patterns and optimized the conditions for the selective alkylation of phenols with terpenoids in the presence of organoaluminum compounds and the rearrangement of phenylisobornyl ether using various catalysts. Gossypol and some of its derivatives are very active inhibitors of radical reactions (oxidation, polymerization, etc.), it is important to note that the effective concentrations of gossypol are significantly lower than its toxic

ISSN: 2582-4686 SJIF 2021-3.261,SJIF 2022-2.889,
2024-6.875 ResearchBib IF: 9.948 / 2024

THE MULTIDISCIPLINARY JOURNAL OF SCIENCE AND TECHNOLOGY

VOLUME-5, ISSUE-3

level. The hydroxyl groups at position 1 and 1′ are relatively inert. Aldehyde groups in the gossypol molecule enhance the inhibitory effect[8-10].


2. Experimental part

2.1. Study of the reaction between gossypol and epichlorohydrin (GECH).


The technology for the production of gossypol with epichlorohydrin (ECH) was carried out in two ways: in the presence of 1% phosphoric acid and 0.5% alkali solution in a molar ratio of gossypol: alkali = 1:2.

The oligomeric product obtained in the presence of phosphoric acid has the following characteristics: it is a homogeneous brown powder, has an average molecular weight of 2300-3500, is non-volatile, main component content of 99.6%.

Reaction scheme according to the first method:

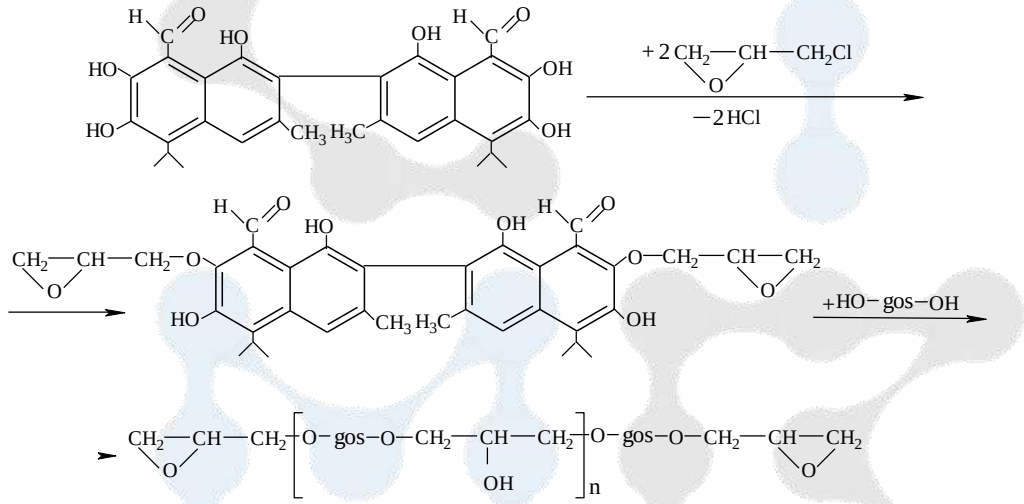


The technology for the synthesis of oligomeric antioxidant based on gossypol and ECH was also carried out in an aqueous solution in the presence of alkali[7]. The reaction is accompanied by the interaction of the hydroxyl groups of gossypol at position 7,7′ with the epoxy groups of epichlorohydrin. The reaction scheme can be represented as follows:

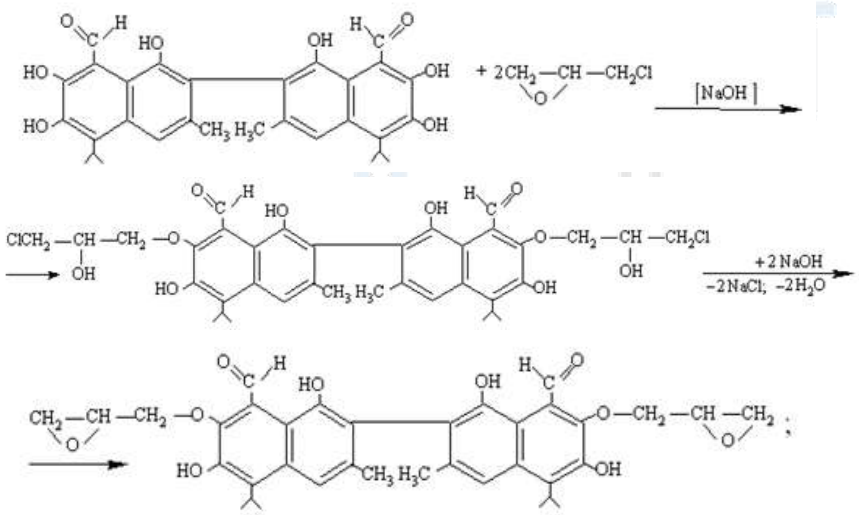

ISSN: 2582-4686 SJIF 2021-3.261,SJIF 2022-2.889,
2024-6.875 ResearchBib IF: 9.948 / 2024

THE MULTIDISCIPLINARY JOURNAL OF SCIENCE AND TECHNOLOGY

VOLUME-5, ISSUE-3

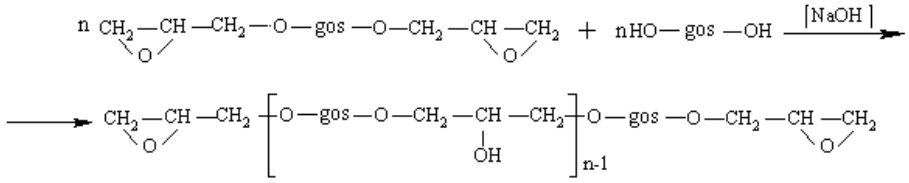

where gos — residue of gossypol.

From the above diagram it is clear that diepoxide derivatives of gossypol and the same amount of gossypol can interact to form oligomers based on them.

The oligomeric product of the interaction of gossypol with ECH, obtained in an alkaline medium, has the following characteristics: homogeneous brown powder, average molecular weight 2500-3800, non-volatile, content of the main component 99.7%.

Results and Its Discussion

IR spectr analysis.

The structure of this compound was confirmed by IR, ^{1}H NMR, spectral and elemental analysis. For comparison, IR spectra of gossypol and its oligomeric derivatives GECH were taken.

The IR spectrum of gossypol (Fig. 2.1 attached in the appendix) contains bands in the region of 3540 and 3510 cm^{-1}, corresponding to free phenolic groups, bands in the region of 3510–3400 cm^{-1} relate to stretching vibrations of the –OH group, some characteristic frequencies of hydroxyl groups are closely related to the formation of intramolecular hydrogen bonds. In practice, the most important is the band of stretching vibrations of the νOH group in the region of 3200–3100 cm^{-1}, and in the range of 1210–1260 cm^{-1} there are bands attributed to free bending vibrations of the phenolic OH group, and also in the region of 1500 cm^{-1} a narrow peak shifts to higher frequencies with increased hydrogen bonding. The bands belonging to (-CH-) groups fluctuate in the range of 3000 and 1429 cm^{-1}. Stretching vibrations of the methyl group (-CH_3) are expressed in the region of 2960 cm^{-1}, and those related to bending vibrations are expressed by narrow bands in the range of 1361 and 1316 cm^{-1}. Weak bands attributed to the isopropyl groups of gossypol appear in the region of 1145 cm^{-1} with a shoulder of 1170 cm^{-1}. The bands in the region of 1620 - 1640 cm^{-1} are due, respectively, to the stretching vibrations of the groups (–C=O). Characteristic bands related to aldehyde groups appear in the region of 1725 cm^{-1} and 1000 cm^{-1}.

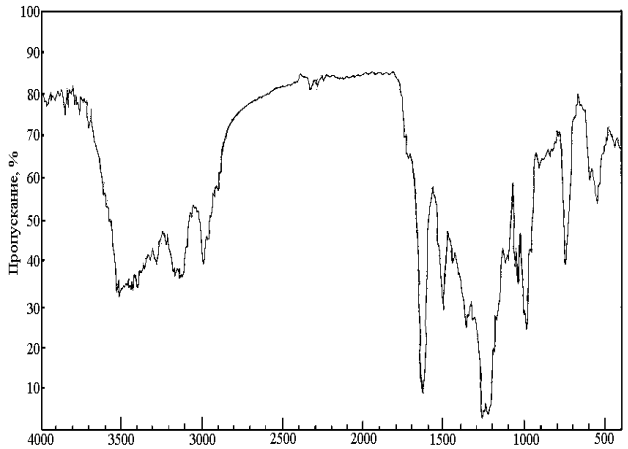


Figure-2.1. IR-spectrum of gossypol.

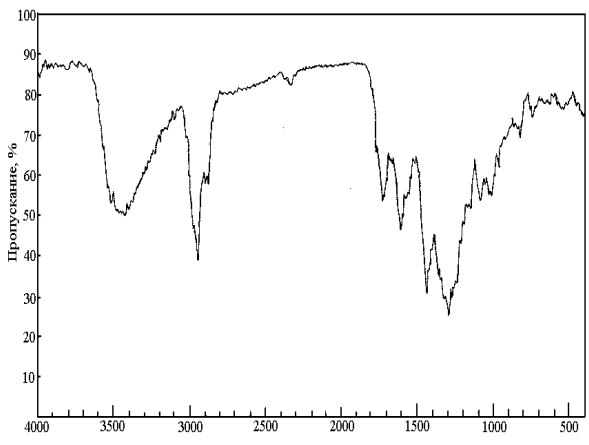


Figure 2.2. IR spectrum of the antioxidant


ISSN: 2582-4686 SJIF 2021-3.261,SJIF 2022-2.889,
2024-6.875 ResearchBib IF: 9.948 / 2024

THE MULTIDISCIPLINARY JOURNAL OF SCIENCE AND TECHNOLOGY

VOLUME-5, ISSUE-3

When studying the IR spectra of the oligomeric antioxidant GECH (Fig. 2), new bands were discovered, appearing in the form of a triplet in the range of 2980, 2950 and 2875 cm^{-1}, a position not characteristic for aromatic ethers.

Characteristic bands for aromatic ethers, expressing asymmetric stretching vibrations of =C–O–C groups, can be seen in the region of 1440 cm^{-1}, 1340 cm^{-1} and the range 1240 – 1275 cm^{-1}. Weak bands in the region of 1180 and 1150 cm^{-1} indicate pendulum vibrations, corresponding to aromatic ethers, and in connection with this, symmetrical stretching vibrations of =C–O–C groups are also expressed in the range of 1020 and 1080 cm^{-1}. In the spectrum of HECH, aldehyde groups of the aromatic ring are clearly observed in the range of 1725 – 1730 cm^{-1}; in the spectrum of gossypol, this peak is covered due to intramolecular hydrogen bonds (Fig. 2.1). The disappearance of intramolecular hydrogen bonds in the HECH spectra in the range of 3100–3200 cm-1 in the form (OH···O=C), which are expressed in the spectra of gossypol (Fig. 2.2), and the appearance of new absorption bands in the regions of 1440 cm^{-1}, 1340 cm^{-1} and the range 1240–1275 cm^{-1}, corresponding to the =C–O–C stretching vibrations, prove that new bands appear in the gossypol molecule, attributed to aromatic ethers of the oligomeric antioxidant GECH.

To record the 1H NMR spectra of the synthesized substances, CD_3COOD was used as a solvent. When studying the ^1H NMR spectrum of the oligomeric antioxidant (Fig. 2.3), new signals appear at 3.57, 3.62 and 3.74 ppm, corresponding to CH_2–O bonds, hydroxyl-containing signals at 4.15 and 4.28 ppm., corresponding to CH–OH bonds. Bands related to epoxy groups appear at 4.7, 4.9, 5.03 and 5.28 ppm, corresponding to  the groups.

^1H NMR spectrum *analysis.*

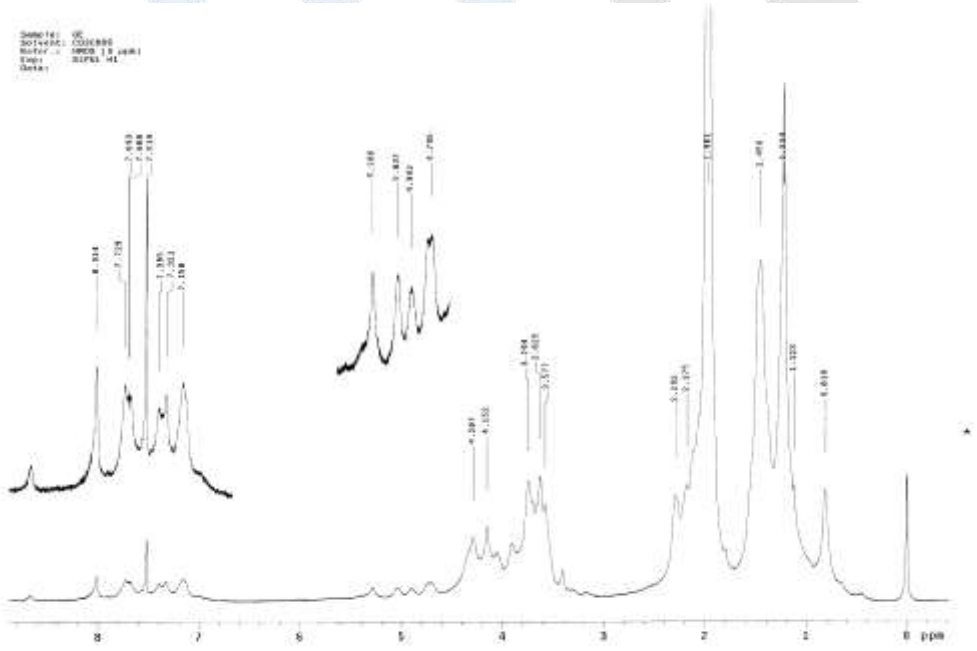


Figure. 2.3. ^1H NMR spectrum of the oligomeric antioxidant GECH.

ISSN: 2582-4686 SJIF 2021-3.261,SJIF 2022-2.889,
2024-6.875 ResearchBib IF: 9.948 / 2024

THE MULTIDISCIPLINARY JOURNAL OF SCIENCE AND TECHNOLOGY

VOLUME-5, ISSUE-3

Elemental analysis of the synthesized oligomer gave the following result (%): C - 68.8; N - 5.12; O - 24.7. The theoretically calculated elemental composition of HECH based on the above structure is as follows (%): C - 68.1; N - 5.76; O - 25.1.

The reaction of gossypol with epichlorohydrin and allyl compounds is characterized by a complex development of the process, due to the presence of various reactive functional groups.

The technological regime of the optimal conditions for the synthesis of gossypol with epichlorohydrin is carried out at a molar ratio of 1:1 in the temperature range of 313–353 K in an alcohol solution. The kinetics of the process was monitored by changes in the concentration of chlorine ions in the reaction mass as the reaction progressed[8].

Table 2.1.

The influence of the molar ratio of reagents on the composition of the product when preparing the oligomeric antioxidant GECH. (T = 338 K τ = 2 h).

Mole ratio: gossypol:ECH	Yield, %	Average mol. mass (cryoscopic)	Elemental analysis, %			
			Carbon		Hydrogen	
			Calculated	Found	Calculated	Found
3:1	72,3	2380	69,1	68,1	5,7	4,8
2:1	87,7	3450		67,9		5,2
1:1	98,8	4860		68,8		5,1
1:2	85,6	3820		69,3		4,9
1:3	79,2	3340		69,2		4,5

The results presented in Fig. 2.4 show that when gossypol interacts with epichlorohydrin in the presence of 1% phosphoric acid, as in the esterification of other polyhydric alcohols, first there is a rapid interaction of the hydroxyl groups of gossypol with the epoxy groups of epichlorohydrin, the rate of which does not depend on a temperature change of 10-20 ° C , then a relatively slow migration of ether formation in the subsequent period.

In this case, the temperature increases to 353 K, as can be seen from Fig. 2.3, leads to an intensification of the oligomerization reaction. Research results show that with increasing temperature, the reaction rate increases by 1.13-1.32 times.

Conclusion

(i). Methods have been proposed for the production of antioxidants based on gossypol with epichlorohydrin compounds under various conditions and ratios of reagents.

(ii). Using IR spectroscopy, mass chromatography, ^{1}H NMR and differential thermal analysis, etc. The inhibitory activity of the synthesized oligomers in PE destruction reactions was studied. It was revealed that the synthesized oligomers based on gossypol prevent thermal-oxidative aging of polymers and are practically superior in efficiency to the antioxidant «Irganox-1010».used in industry.

(iii). The kinetics of oxygen absorption by the original and stabilized LDPE was studied at different molecular oxygen pressures. It has been established that, along with reactions of inhibition of the polymer oxidation process, the oligomeric antioxidant leads to inhibition of the process of destruction of the polymer composition.

(iv). According to the obtained results, the amount of antioxidant based on gossypol and epichlorhydrin showed the highest thermal and mechanical strength when the amount was 0.2%.

ISSN: 2582-4686 SJIF 2021-3.261,SJIF 2022-2.889,
2024-6.875 ResearchBib IF: 9.948 / 2024

THE MULTIDISCIPLINARY JOURNAL OF SCIENCE AND TECHNOLOGY

VOLUME-5, ISSUE-3

References

1. Kalugina E.V., Ivanov A.N., Tochin V.A. Approaches to the stabilization of composite polymer materials // Plast, masses. - 2006. - No. 10. - P. 30.

3. Borukaev T.A., Mashukova B.S., Mashukov N.I., Tlenkopachev M.A., Mikitaev A.K. Physico-mechanical properties of polybutylene terephthalate modified with polyazomethine // Plast, masses. - 2004. - No. 4. - P.18-19.

4. Doss, A., Pugalenthi, M., Vadivel, V. Antioxidant activity of raw and differentially processed under-utilized tropical legume Canavalia Ensiformis L. DC seeds, South India/ IOAB Journal. Vol. 2, Is. 8, 2012, P. 27-32.

5. Boo, H.-O., Hwang, S.-J., Bae, C.-S., Park, S.-H., Heo, B.-G., Gorinstein, S. Extraction and characterization of some natural plant pigments/Industrial Crops and Products. Vol. 40, Is. 1, 2012, P. 129-135.

6. P.Cerruti, M.Malinconico, J.Rychly, L.Matisova-Rychla, C.Carfagna. Effect of natural antioxidants on the stability of polypropylene films. //Polymer Degradation and Stability, 2009, т. 94, -C. 2095.

7.Nurilloev Zafar, Beknazarov Khasan and Nomozov Abror, "Production of Corrosion Inhibitors Based on Crotonaldehyde and Their Inhibitory Properties," *International Journal of Engineering Trends and Technology*., 2022, vol. **70**, 8, pp. 423-434,

8.Nomozov A.K. Beknazarov Kh, Khodjamkulov S, Misirov Z, Yuldashova S. Synthesis of Corrosion Inhibitors Based on (Thio)Urea, Orthophosphoric Acid and Formaldehyde and Their Inhibition Efficiency. Baghdad Sci.J. 2024; 22(4). https://doi.org/10.21123/bsj.2024.10590.

9. Abror Nomozov. Studying of The Process of Obtaining Monocalcium Phosphate based on Extraction Phosphoric Acid from Phosphorites of Central Kyzylkum. *Baghdad Sci.J* (1)2024.

10. A.Nomozov et al. Studying of The Process of Obtaining Monocalcium Phosphate based on Extraction Phosphoric Acid from Phosphorites of Central Kyzylkum. Baghdad Science Journal, 22(2024), 756-775. https://doi.org/10.21123/bsj.2024.9836.

11.Durdibaeva, R., Beknazarov, K., Nomozov, A., Demir, M., Berdimurodov, E. Exploring protective mechanisms with triazine ring andhydroxyethyl groups: experimental and theoretical insights. *Kuwait Journal of Science*. 2024, Vol. 52, p 100341. https://doi.org/10.1016/j.kjs.2024.100341.

12. A. Muqimov, Kh.Kh. Turaev. Modern approach to the addition of organomineral additives to increase cement brand. A review. *Chemical Review and Letters*. 7(2024) 804-815. https://doi.org/10.22034/crl.2024.467805.1381.

13.Nomozov, S.Ch. Eshkaraev, Z.E.Jumaeva, J.N.Todjiev, S.S.Eshkoraev, F.A. Umirqulova. Experimental and Theoretical Studies of ***Salsola oppositifolia*** Extract as a Novel Eco-Friendly Corrosion Inhibitor for Carbon Steel in 3% NaCl. **Inter. Journal of Eng. Trends and Tech. 72(2024). 312-320. https://doi.org/10.14445/22315381/IJETT-V72I9P126.**

14. Nomozov A, K, et.all. Salsola Oppositifolia acid extract as a green corrosion inhibitor for carbon steel. Indian Journal of Chemical Technology. 2023, 30, 872-877. https://doi.org/10.56042/ijct.v30i6.6553.